

Superior DC and RF Performance of AlGaN-Channel HEMT at High Temperatures

メタデータ	<p>言語: English</p> <p>出版者:</p> <p>公開日: 2013-05-31</p> <p>キーワード (Ja):</p> <p>キーワード (En):</p> <p>作成者: HATANO, Maiko, YAFUNE, Norimasa, TOKUDA, Hirokuni, YAMAMOTO, Yoshiyuki, HASHIMOTO, Shin, AKITA, Katsushi, KUZUHARA, Masaaki</p> <p>メールアドレス:</p> <p>所属:</p>
URL	<p>http://hdl.handle.net/10098/7419</p>

Superior DC and RF Performance of AlGa_N-Channel HEMT at High Temperatures

Maiko HATANO^{†a)}, Student Member, Norimasa YAFUNE^{††}, Nonmember, Hirokuni TOKUDA[†], Member, Yoshiyuki YAMAMOTO^{†††}, Shin HASHIMOTO^{†††}, Katsushi AKITA^{†††}, Nonmembers, and Masaaki KUZUHARA[†], Senior Member

SUMMARY This paper describes high-temperature electron transport properties of AlGa_N-channel HEMT fabricated on a free-standing AlN substrate, estimated at temperatures between 25 and 300°C. The AlGa_N-channel HEMT exhibited significantly reduced temperature dependence in DC and RF device characteristics, as compared to those for the conventional AlGa_N/Ga_N HEMT, resulting in larger values in both saturated drain current and current gain cutoff frequency at 300°C. Delay time analyses suggested that the temperature dependence of the AlGa_N-channel HEMT was primarily dominated by the effective electron velocity in the AlGa_N channel. These results indicate that an AlGa_N-channel HEMT fabricated on an AlN substrate is promising for high-performance device applications at high temperatures.

key words: AlGa_N channel, high temperature, HEMT

1. Introduction

GaN-based HEMTs are expected as promising devices for high-voltage, high-frequency and high-temperature electronic applications. With an ability to exhibit extremely reduced intrinsic carrier concentration, DC characteristics of AlGa_N/Ga_N HEMTs at elevated temperatures have been reported by many authors [1]–[7]. Kordos et al. reported that with increasing the device temperature to more than 200°C, the saturated drain current of a 2 μm gate-length AlGa_N/Ga_N HEMT decreased to below one half of that measured at room temperature [6]. It is evident that the temperature dependence in the DC characteristics of GaN-based HEMTs should be further improved to ensure stable device operation at high temperatures.

Recently, a novel nitride-based HEMT structure, in which AlGa_N is used as a channel layer, has been proposed [8]–[13]. Nanjo et al. demonstrated that a drain breakdown voltage as high as 1650 V was achieved for an AlGa_N-channel HEMT with an Al composition of 38% [9]. Tokuda et al. reported that the degradation in the drain current by increasing the device temperature from room temperature (RT) to 300°C was significantly suppressed within 20% by using an AlGa_N channel with an Al composition of 51% [11]. However, the magnitude of the drain current at 300°C

was still larger for the conventional AlGa_N/Ga_N HEMT than that for the AlGa_N-channel device, and no data have been reported on the high-temperature RF performance for the AlGa_N-channel HEMT.

In this paper, DC and RF performance of AlGa_N-channel HEMTs fabricated on an AlN substrate is presented. The maximum drain current and the current gain cutoff frequency measured at temperatures from RT to 300°C are compared between devices with an AlGa_N channel and a Ga_N channel. The mechanism responsible for the superior performance for the developed AlGa_N-channel HEMT at high temperatures is discussed.

2. Device Fabrication

Figure 1 shows the schematic diagram of an AlGa_N-channel HEMT fabricated on a free standing C-plane AlN substrate. Epitaxial layers were grown by metal-organic vapor phase epitaxy (MOVPE). The structure consists of a 200-nm-thick AlN buffer, an undoped 600 nm AlGa_N channel layer with an Al composition of 0.26, and an undoped 27 nm AlGa_N barrier layer with an Al composition of 0.50. Device fabrication began with mesa isolation using ICP-RIE based on BCl₃ plasma. Then, the source and drain ohmic contacts were formed using a Zr/Al/Mo/Au metal stack annealed at 950°C for 30 s [14]. The specific ohmic contact resistivity and the sheet resistance, estimated by transmission-line-model (TLM) measurements were $5.0 \times 10^{-4} \Omega \text{cm}^2$ and $4550 \Omega/\text{sq}$, respectively. Ni/Au was used as Schottky gate metallization.

DC characteristics were measured using on-wafer DC probes for a device with a gate length (L_g) of 6 μm and a gate

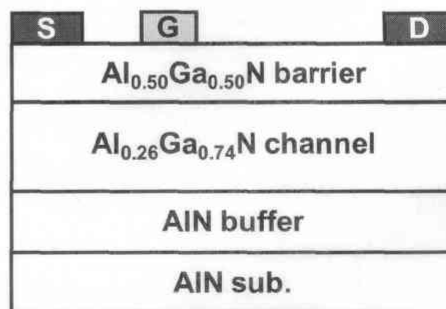


Fig. 1 Schematic cross section of Al_{0.50}Ga_{0.50}N/Al_{0.26}Ga_{0.74}N HEMT on AlN substrate.

Manuscript received November 16, 2011.

Manuscript revised March 6, 2012.

[†]The authors are with the Graduate School of Engineering, University of Fukui, Fukui-shi, 910-8507 Japan.

^{††}The author is with Sharp Corporation, Tenri-shi, 632-8567 Japan.

^{†††}The authors are with Sumitomo Electric Industries, Ltd., Itami-shi, 664-0016 Japan.

a) E-mail: mhatano@u-fukui.ac.jp


DOI: 10.1587/transele.E95.C.1332

width (W_g) of $515\text{ }\mu\text{m}$. S-parameter measurements were performed using on-wafer RF probes from 10 MHz to 4 GHz for a device with $L_g=2\text{ }\mu\text{m}$ and $W_g=2\times 50\text{ }\mu\text{m}$. A standard AlGaIn/GaN HEMT with identical electrode dimension was fabricated on a Si substrate. The thickness and Al composition for the AlGaIn barrier layer were 25 nm and 0.25, respectively. Since the main purpose of this work is to study the importance of channel materials, no surface passivation films were used for all the devices.


3. Results and Discussion

Figures 2(a) and (b) show DC drain I-V characteristics for the fabricated AlGaIn-channel HEMT ($L_g=6\text{ }\mu\text{m}$ and $W_g=515\text{ }\mu\text{m}$) measured at 25°C and at 300°C , respectively. The maximum drain current defined at a gate-to-source bias voltage (V_{gs}) of 2 V was 175 mA/mm at 25°C and was 106 mA/mm at 300°C .

Figure 3 shows the maximum drain current as a func-

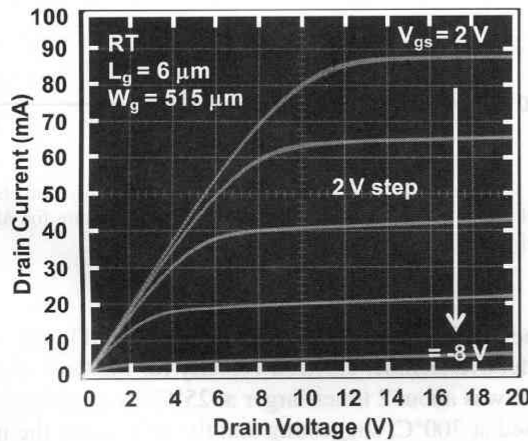

(a)

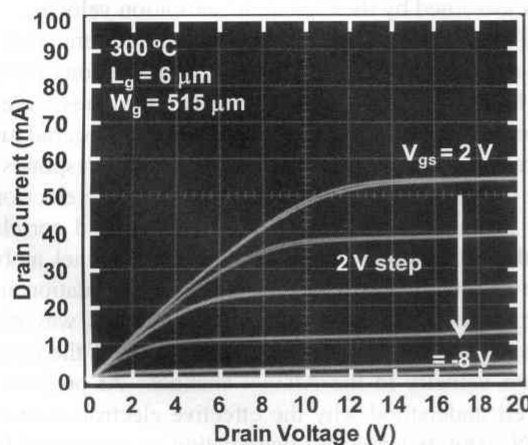

(b)

Fig. 2 Drain I-V characteristics for AlGaIn-channel HEMT with $L_g = 6\text{ }\mu\text{m}$ and $W_g = 515\text{ }\mu\text{m}$ at (a) RT and (b) 300°C .

tion of temperature for the AlGaIn-channel HEMT and for the conventional AlGaIn/GaN HEMT. The maximum drain current for the GaN-channel HEMT decreased from 281 mA/mm at 25°C to 97 mA/mm at 300°C , corresponding to about 65% degradation. Similar degradation trend has been observed for AlGaIn/GaN HEMT fabricated on a sapphire substrate, suggesting that the substrate thermal conductivity has minor influence on the comparison of drain current at high temperatures. On the other hand, the degradation for the AlGaIn-channel device was only 40%. Therefore, although the maximum drain current at RT was smaller for the AlGaIn channel, its magnitude was reversed with each other at around 250°C . At 300°C , the maximum drain current for the AlGaIn-channel HEMT was about 10% larger than that for the GaN-channel HEMT. This is the first report demonstrating that an AlGaIn-channel HEMT, having identical device dimension, shows better DC characteristics than AlGaIn/GaN HEMTs when estimated at high temperatures.

In order to investigate the mechanism for the reversal in drain current observed between GaN and AlGaIn channels, temperature dependent Hall-effect measurements have been performed using the van der Pauw method. Figure 4 shows the Hall mobility measured from RT to 300°C for heterostructures with an AlGaIn channel and with a conventional GaN channel. It was found that the channel mobility decreased monotonically with the increase in temperature for both channel materials, indicating that no reversal in the magnitude of channel mobility occurred between the samples at temperatures up to 300°C .

Figure 5 shows temperature dependence of the current gain cutoff frequency for AlGaIn-channel and GaN-channel HEMTs ($L_g=2\text{ }\mu\text{m}$ and $W_g=100\text{ }\mu\text{m}$) estimated by on-wafer S-parameter measurements. Devices were biased at $V_{gs}=0\text{ V}$ and at a drain-to-source voltage (V_{ds}) of 25 V. The current gain cutoff frequency was estimated by extrapolating current gain (h_{21}) using -20 dB/dec roll-off. S-parameters at each frequency were used after de-embedding parasitic pad capacitance and inductance [15]. The current gain cutoff frequency monotonically decreased with increasing tempera-

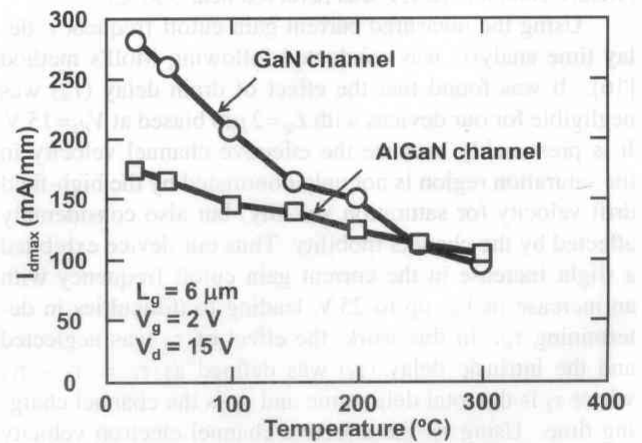


Fig. 3 Maximum drain current (I_{dmax}) as a function of temperature for AlGaIn-channel HEMT and for GaN-channel HEMT.

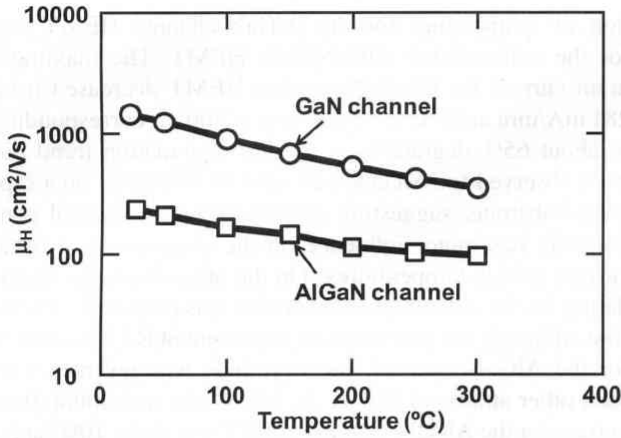


Fig. 4 Temperature dependence of Hall mobility for devices with AlGaIn channel and GaN channel.

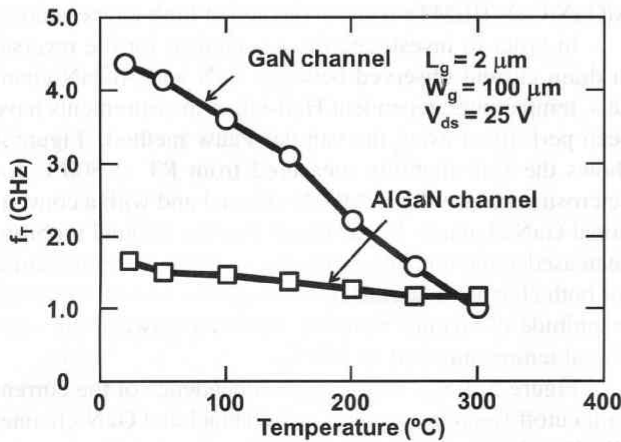


Fig. 5 Current gain cutoff frequency (f_T) as a function of temperature for AlGaIn-channel HEMT and for GaN-channel HEMT with $L_g=2\mu\text{m}$ and $W_g=100\mu\text{m}$.

ture in both devices. However, it is obvious that the decrease ratio for the AlGaIn-channel HEMT is extremely smaller than that for the GaN-channel HEMT. More interestingly, the magnitude of the current gain cutoff frequency for the AlGaIn-channel HEMT was reversed near 300°C .

Using the measured current gain cutoff frequency, delay time analysis was conducted following Moll's method [16]. It was found that the effect of drain delay (τ_d) was negligible for our devices with $L_g=2\mu\text{m}$ biased at $V_{ds}=15\text{V}$. It is presumably because the effective channel velocity in the saturation region is not only dominated by the high-field drift velocity (or saturation velocity) but also considerably affected by the channel mobility. Thus our device exhibited a slight increase in the current gain cutoff frequency with an increase in V_{ds} up to 25 V, leading to difficulties in determining τ_d . In this work, the effect of τ_d was neglected and the intrinsic delay (τ_i) was defined as $\tau_i = \tau_t - \tau_c$, where τ_t is the total delay time and τ_c is the channel charging time. Using τ_i , the effective channel electron velocity was derived by L_g/τ_i . Table 1 shows the effective channel electron velocity estimated at 25 and 300°C for an AlGaIn-

Table 1 Effective channel electron velocity of AlGaIn-channel HEMT and GaN-channel HEMT evaluated at 25°C and at 300°C .

	$v_{\text{eff}}@25^\circ\text{C}$ (10^6cm/s)	$v_{\text{eff}}@300^\circ\text{C}$ (10^6cm/s)
AlGaIn channel	2.7	1.7
GaN channel	6.0	1.5

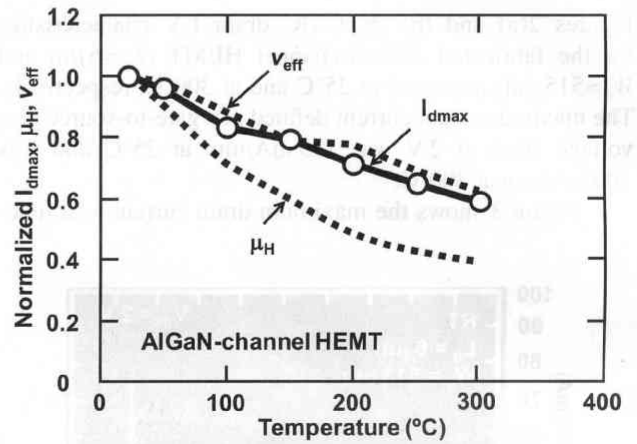


Fig. 6 Normalized maximum drain current, Hall mobility, and effective channel electron velocity (v_{eff}) as a function of temperature for AlGaIn-channel HEMT.

channel HEMT and for a GaN-channel HEMT. Although the effective channel electron velocity for the GaN-channel HEMT was about 2 times larger at 25°C , its magnitude was reversed at 300°C , suggesting that the reversal of the maximum drain current observed at high temperatures, as shown in Fig. 3, was closely related to the temperature dependence of the effective channel electron velocity that was predominantly governed by the high-field saturation velocity.

Figure 6 shows the maximum drain current, Hall mobility, and effective electron velocity as a function of temperature for the AlGaIn-channel HEMT. All values were normalized to those at 25°C . It is evident that the degradation in the drain current at elevated temperatures corresponds well to the temperature dependence of the effective electron velocity in the channel and does not show good correlation with the temperature dependence of the channel mobility. These results suggest that the reduced degradation in the maximum drain current at high temperatures was mainly dominated by the temperature dependence of the effective electron velocity in the AlGaIn channel. At present, it is not well understood why the effective electron velocity in AlGaIn exhibited reduced degradation as compared to the temperature dependence of the channel mobility. In our devices with $L_g=2\mu\text{m}$, all the channel region under the gate would not be in such enough high electric fields to allow all the channel electrons moving with a high-field (saturated)

electron velocity. The slight deviation observed between the temperature dependences of effective electron velocity and maximum drain current, in Fig. 6, may be due to the fact that some of the channel electrons are still affected by the low-field mobility though they are mostly accelerated by the high electric field in the channel region. To clarify the mechanism in more details, it would be desirable to perform similar experiments on shorter gate length HEMTs, where high-field transport is dominant under the whole gate region.

4. Conclusion

An AlGa_N-channel HEMT has been fabricated on a free-standing AlN substrate and its device performance has been compared to that for a standard AlGa_N/Ga_N HEMT. At room temperature, the conventional Ga_N-channel HEMT exhibited much better performances in most of the device properties, such as maximum drain current, channel electron mobility, current gain cutoff frequency, and effective electron velocity, than those for the AlGa_N-channel HEMT. However, the difference in those properties was reduced with increasing the device temperature. At 300°C, the magnitude of the maximum drain current and the current gain cutoff frequency was reversed between the two devices, showing that an AlGa_N-channel HEMT is superior to a conventional AlGa_N/Ga_N HEMT at high temperatures. These results indicate that an AlGa_N-channel HEMT on an AlN substrate is promising for high-temperature electronics applications at more than 300°C. The superior high-temperature performance of AlGa_N-channel HEMTs is presumed to be due to the comparatively small temperature dependence in electron drift velocity at high fields.

Acknowledgments

This work was performed as a part of the project named "Development of Nitride-based Semiconductor Single Crystal Substrate and Epitaxial Growth Technology" by NEDO. This work was also supported by a grant from the Global COE Program, "Center for Electronic Devices Innovation", from the Ministry of Education, Culture, Sports, Science and Technology of Japan.

References

- [1] O. Aktas, Z.F. Fan, S.N. Mohammad, A.E. Botchkarev, and H. Morkoc, "High temperature characteristics of AlGa_N/Ga_N modulation doped field-effect transistors," *Appl. Phys. Lett.*, vol.69, pp.3872–3874, 1996.
- [2] R. Gaska, Q. Chan, J. Yang, A. Osinsky, M.A. Khan, and M.S. Shur, "High-temperature performance of AlGa_N/Ga_N HFET's on SiC substrates," *IEEE Electron Device Lett.*, vol.18, no.10, pp.492–494, 1997.
- [3] N. Maeda, T. Saitoh, K. Tsubaki, T. Nishida, and N. Kobayashi, "Superior pinch-off characteristics at 400°C in AlGa_N/Ga_N heterostructure field effect transistors," *Jpn. J. Appl. Phys.*, vol.38, pp.L987–L989, 1999.
- [4] T. Egawa, H. Ishikawa, and M. Umeno, "Recessed gate AlGa_N/Ga_N modulation-doped field-effect transistors on sapphire," *Appl. Phys. Lett.*, vol.76, pp.121–123, 2000.
- [5] S. Arulkumaran, T. Egawa, H. Ishikawa, and T. Jimbo, "High-temperature effects of AlGa_N/Ga_N high-electron-mobility transistors on sapphire and semi-insulating SiC substrates," *Appl. Phys. Lett.*, vol.80, pp.2186–2188, 2002.
- [6] P. Kordos, D. Donoval, M. Florovic, J. Kovac, and D. Gregusova, "Investigation of trap effects in AlGa_N/Ga_N field-effect transistors by temperature dependent threshold voltage analysis," *Appl. Phys. Lett.*, vol.92, 152113, 2008.
- [7] R. Cuervo, F. Calle, A.F. Brana, Y. Cordier, M. Azize, N. Baron, S. Chenot, and E. Munoz, "High temperature behavior of Ga_N HEMT devices on Si(111) and sapphire substrates," *Phys. Stat. Sol. (c)*, vol.5, pp.1971–1973, 2008.
- [8] T. Nanjo, M. Takeuchi, M. Suita, Y. Abe, T. Oishi, Y. Tokuda, and Y. Aoyagi, "First operation of AlGa_N channel high electron mobility transistors," *Appl. Phys. Express* 1, 011101, 2008.
- [9] T. Nanjo, M. Takeuchi, M. Suita, Y. Abe, T. Oishi, Y. Tokuda, and Y. Aoyagi, "Remarkable breakdown voltage enhancement in AlGa_N channel HEMTs," *IEDM. Tech. Dig.*, pp.397–400, 2007.
- [10] A. Raman, S. Dasgupta, S. Rajan, J.S. Speck, and U.K. Mishra, "AlGa_N channel high electron mobility transistors: Device performance and power-switching figure of merit," *Jpn. J. Appl. Phys.*, vol.47, pp.3359–3361, 2008.
- [11] H. Tokuda, M. Hatano, N. Yafune, S. Hashimoto, K. Akita, Y. Yamamoto, and M. Kuzuhara, "High Al composition AlGa_N-channel high-electron-mobility transistor on AlN substrate," *Appl. Phys. Express* 3, 121003, 2010.
- [12] M. Hatano, N. Kunishio, H. Chikaoka, J. Yamazaki, Z.B. Makhzani, N. Yafune, K. Sakuno, S. Hashimoto, K. Akita, Y. Yamamoto, and M. Kuzuhara, "Comparative high-temperature DC characterization of HEMTs with Ga_N and AlGa_N channel layers," *CS MANTECH Conf., Dig.*, pp.101–104, 2010.
- [13] M. Hatano, J. Yamazaki, N. Yafune, S. Hashimoto, K. Akita, Y. Yamamoto, and M. Kuzuhara, "High-temperature RF characterization of AlGa_N-channel HEMTs," 9th Topical Workshop on Heterostructure Microelectronics (TWHM2011), *Dig.*, pp.13–14, 2011.
- [14] N. Yafune, S. Hashimoto, K. Akita, Y. Yamamoto, and M. Kuzuhara, "Low-resistive ohmic contacts for AlGa_N channel high-electron-mobility transistors using Zr/Al/Mo/Au metal stack," *Jpn. J. Appl. Phys.*, vol.50, 100202, 2011.
- [15] Q. Fan, J.H. Leach, and H. Morkoc, "Small signal equivalent circuit modeling for AlGa_N/Ga_N HFET: Hybrid extraction method for determining circuit elements of AlGa_N/Ga_N HFET," *Proc. IEEE*, vol.98, pp.1140–1150, 2010.
- [16] N. Moll, M.R. Hueschen, and A.F. Colbrrie, "Pulse-doped AlGaAs/InGaAs pseudomorphic MODFET's," *IEEE Trans. Electron Device.*, vol.35, no.7, pp.879–885, 1988.



Maiko Hatano received the B.E. and M.E. degrees in Electrical and Electronics Engineering from University of Fukui, Fukui, Japan, in 2009 and 2011, respectively. She is currently working toward the Ph.D. degree in the System Design Engineering Course, University of Fukui, Fukui, Japan.




Norimasa Yafune received the M.S. degree in Physics from Osaka University, Osaka, Japan, in 2003. He is currently working in R&D Laboratories, SHARP corporation, Japan.




Hirokuni Tokuda received the Ph.D. degree in electronics engineering from University of Tokyo, Japan, in 1978. From 1978 to 2002, he worked for Toshiba Corp., where he had been in charge of the development of millimeter-wave HEMTs. In 2002, he moved to Murata Manufacturing Co. Ltd., where he was a general manager of Antenna Products Dept. After the retirement from Murata in 2009, he got the job at University of Fukui. His current interests are GaN-based HEMT devices and their physics.




Yoshiyuki Yamamoto received the B.E. and M.E. degrees in industrial chemistry from University of Tokyo, Japan, in 1990 and 1992, respectively. He has been working for Sumitomo Electric Industries from 1992, where he is in charge of R&D for the bulk crystal growth technique and applications of wide-bandgap semiconductor materials.

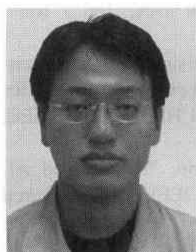

Shin Hashimoto received the M.S. degree in Physics from Osaka University, Osaka, Japan, in 2004. He is currently working in Semiconductor Technologies R&D Laboratories, Sumitomo Electric Industries, Japan.

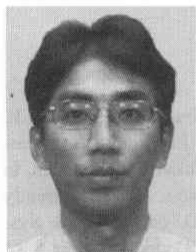

Katsushi Akita received the B.E. and M.E. degrees in physics from Kyoto University, Kyoto, Japan, in 1993 and 1995, respectively. He has been working for Sumitomo Electric Industries from 1995, where he is in charge of R & D for epitaxial growth of compound semiconductors. In 2007, he received the Ph.D. degree in engineering from Kyoto Institute of Technology, Kyoto, Japan. He was awarded JSAP Paper Award in 2010.

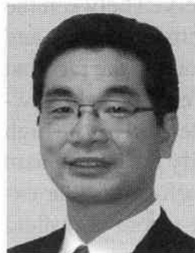

Masaaki Kuzuhara received the B.E., M.E. and Ph.D. degrees in electrical engineering from Kyoto University, Kyoto, Japan, in 1979, 1981 and 1991, respectively. He is currently a Professor in Electrical and Electronics Engineering, University of Fukui, Fukui, Japan. His research interests include III-nitride heterojunction devices for high-voltage and high-frequency applications. He is a Fellow of IEEE.